

AN ANALYSIS OF THE JOINTS' PROPERTIES OF FINE-GRAINED STEEL WELDED BY THE MAG AND SAW METHODS

The article presents an analysis of properties of welded joints of fine-grained steel of P460NH type used more and more often in the modern constructions. A process of examining a technology of welding has been carried out on the thick-walled butt joints of sheet metal by two methods of welding namely MAG – 135 and SAW – 121. The article deals with a topic of optimizing a process of welding thick-walled welded joints of fine-grained steel due to their mechanical properties and efficiency.

Keywords: welding, properties of joints, fine-grained types of steel, non-destructive, and destructive testing, optimizing a process of welding

1. Introduction

At the time of a continuous economy growth there is an increasing need for steel constructions particularly in the following sectors: power engineering and metallurgy. Mentioned need refers mostly to manufacturing huge and heavy welded constructions such as steam turbine castings for conventional and nuclear power plants, or convection heaters for metallurgy. Above constructions are characterised by a great number of thick-walled welded joints. Manufacturers of such constructions often stand in front of a problem which method of welding is the most appropriate to make joints. In order to make a right decision specialists need to possess all the necessary information relating to the technology of welding, characteristics of materials, and also properties of welded joints.

The aim of an article is to take examinations of a technology of welding of thick-walled welded joints made from fine-grained steel standard annealed, and designed for pressure devices. Examination of a welding technology taken according to the PN-EN ISO 15614-1 standard includes a preparation of a technology of welding, and doing destructive and non-destructive tests of welded joints. The most popular methods of welding were used to make sample thick-walled joints namely metal active gas welding in an active gas shield by the solid welding electrode (MAG -135), and submerged arc welding by the solid welding electrode (SAW 121). Results of examinations of welding technologies should provide numerous valuable information, which are vital to make proper decisions while choosing a technology of welding.

2. Characteristics of welding methods

Two methods of welding [1] were used to take an examination of the welding technology i.e.:

- 135 metal active gas welding in an active gas shield by the solid welding electrode (MAG)
- 121 submerged arc welding by the solid welding electrode (SAW).

Above methods fulfil the requirements which are put on thick-walled joints both by means of technology and efficiency.

2.1. Welding by the MAG method

Welding by the MAG (Eng. Metal Active Gas) method refers to melting the edges of the joint's elements and the material of the melting electrode by the heat of an electric arc in the gas shield or a gaseous mixture. A source of the heat is an electric arc, which is arcing in a gaseous atmosphere between a melting electrode and a welded material [2, 3]. Nowadays, welding by the MAG method is used in many different types, and in many forms of transferring a metal in the welding arc [4]. The most popular method 135, which can be used to make high quality joints in the steel constructions, was used to take examinations. Above method allows to obtain proper joints both in respect of technology, and metallurgy for the following types of steel: carbon steel, low-alloyed steel, high-alloyed steel and special-purpose steel. The 135 method is characterised by a possibility to weld in all positions, both a manual and mechanized welding [3].

2.2. Welding by the SAW method

Welding by the submerged arc (Eng. Submerged Arc Welding; SAW) method refers to melting the edges of the joint's elements and the material of the melting electrode by the heat of an electric arc under a layer of granular flux. A source of the heat is an electric arc, which is arcing in a gaseous

* POLITECHNIKA CZĘSTOCHOWSKA, 69 J.H. DĄBROWSKIEGO STR., 42-201 CZĘSTOCHOWA, POLAND

Corresponding author: ryszardkrawczyk@spaw.pcz.pl

atmosphere made of a melted flux between a melting electrode and a welded material [2]. This method is characterised by a high purity of metallurgy, and very good properties of the joints of all types of steel used for welding constructions, as well as other materials. The 121 method is also characterised by the high efficiency of welding, and is often dedicated to make joints of thick-walled elements. It allows to weld only in the flat and horizontal positions of welding in mechanized conditions [5].

3. Materials used for examinations

Metal plates from the 1.3 group according to the PN ISO 15608 [6] of the P460NH type according to the PN EN 10028-3 [7] standard were used for examinations as the basic materials. Above materials belong to the welding type of steel, fine-grained, standard annealed to use in elevated temperatures, intended to use inter alia in pressure devices. Normalized fine-grained types of steel are characterised by the thigh mechanical properties, and due to a high carbon equivalent (higher content of manganese, and a presence of other elements) are more susceptible to harden in the HAZ than low carbon types of

steel [8-16]. What is more, they are more exposed to form cold cracks [17-25]. Thus, it is recommended to follow these rules:

- to reduce an amount of a diffused hydrogen inserted into the weld by removing contaminations, rust, and moisture from an area of welding, as well as using a low-hydrogen welding processes,
- to use heating elements of greater thickness in order to avoid creating martensite in the HAZ,
- to use appropriate technological solutions in order to reduce shrinkage stresses [8, 26-27].

If the following requirements are fulfilled than we can accept that special safety regulations are not required assuming that a low-hydrogen process of welding was used for steel of $R_m = 490 - 690$ MPa resistance (recommendations of the International Welding Institute)

$$C \leq 0,20\% \text{ i } Ce \leq 0,45\% \text{ and } g \leq 25\text{mm}$$

Or

$$C \leq 0,20\% \text{ i } Ce \leq 0,41\% \text{ and } 25 < g \leq 37\text{mm}$$

In the fine-grained types of steel there is a limited growth of austenite grains in the HAZ. It is caused by the

TABLE 1

Chemical composition (a ladle chemical analysis) [7]

Type of steel		% weight														
symbol	No.	C max	Si max	Mn	P max	S max	Al total min	N max	Cr max	Cu max	Mo max	Nb max	Ni max	Ti max	V max	Nb+Ti+V max.
P460NH	1.8935	0,20	0,60	1,10 do 1,70	0,025	0,015	0,020	0,025	0,30	0,70	0,10	0,05	0,80	0,03	0,20	0,22

TABLE 2

Mechanical properties in an ambient temperature [7]

Type of steel		Regular state of delivery	Thickness of the material t [mm]	Boundary of plasticity R_{eH} min. [MPa]	Tensile strength R_m [MPa]	Elongation after breaking A min. [%]
Symbol	Number					
P460NH	1.8935	+N	≤ 16	460	570 to 720 ^b	17
			$16 < t \leq 40$	445		
			$40 < t \leq 60$	430		
			$60 < t \leq 100$	400	540 to 710	
			$100 < t \leq 250$	a	a	

^a values can be agreed while inquiring about an offer and ordering

^b there is a permissible maximum value of 730 MPa for products of 16mm thick

TABLE 3

Minimal impact values [7]

Type of steel	Thickness of a product [mm]	Work of fracture KV [J] min									
		Transverse					longitudinal ^a				
		- 50	- 40	- 20	0	+20	- 50	- 40	- 20	0	+ 20
P460NH	5 do 100	-	-	30	40	50	-	-	45	65	75

^a Above values refer to products of 40 mm thick

precipitations of carbides, nitrides or carbonitrides of micro-alloyed elements. Fine-grained austenite while changing in the process of melting of welded joint makes structures of high impact value. A general characteristics of fine-grained type of steel used in the P460NH examinations is presented in the tables 1, 2 and 3.

Meeting the requirements of the PN-EN 10028-3 standard allows to presume a compatibility with appropriate requirements of the 97/23/WE pressure directive. Steel produced according to the above standard can be used to make pressure devices, which can be exploited in the European Union.

4. Examinations of a technology of welding

Certain examinations of sample welded joints were taken in order to make an assessment of a technology of welding taking into account acceptance criteria included in the standard, which relates to an examination of a technology of welding namely

the PN-EN ISO 15614-1 standard. Examinations were taken on the sample joints made according to the initial technology conditions for the MAG and SAW methods of welding.

4.1. Sample welded joints

The PN-EN ISO 15614-1 standard describes requirements relating to an assessment of an initial manual welding technology by means of examinations taken on the sample joints. Sample joints for examinations were prepared from the P460NH steel of 40mm thick metal plates with an X bevelled for a double-sided butt welding according to the requirements of the mentioned standard. There were two joints measuring 300x350mm for welding by the 135 method in order to make sample joints in two positions horizontal – PC, and vertical upwards progression - PF positions. For welding by the 121 method a joint measuring 300x700mm was prepared. An initial manual welding technology for making sample joints

TABLE 4

Details relating to the MAG method in the horizontal position - PC

Bead sequence	Welding process	Filler metal size [mm]	Current [A]	Voltage [V]	Travel speed [cm/min]	Polarity	Heat input [KJ/cm]
1	135	1,2	140-160	17-20	18-22	DC/+	5,2-5,8
2	135	1,2	180-200	20-21	24-25	DC/+	5,9-6,5
3-n	135	1,2	200-240	21-24	25-30	DC/+	6,5-7,5
1'	135	1,2	180-200	20-21	24-25	DC/+	5,9-6,5
2-n'	135	1,2	200-240	21-24	25-30	DC/+	6,5-7,5
Solid wire-classification: G2Mo according to the EN ISO 14341-A (OK AristoRod 13.09)							
Shielding gas type: Ferromix C18 – M21 according to the PN-EN ISO 14175							
Gas flow rate: [l/min]: 14 - 18				Preheat temperature: $\geq 100^{\circ}\text{C}$			
Heat treatment: not applicable				Interpass temperature: $\leq 250^{\circ}\text{C}$			

TABLE 5

Details relating to the MAG method in the vertical upwards progression PF

Bead sequence	Welding process	Filler metal size [mm]	Current [A]	Voltage [V]	Travel speed [cm/min]	Polarity	Heat input [KJ/cm]
1	135	1,2	120-140	16-18	12-16	DC/+	6,2-6,1
2	135	1,2	180-220	20-22	16-18	DC/+	8,7-10,5
3-n	135	1,2	200-240	21-24	16-18	DC/+	10,1-12,5
1'	135	1,2	180-220	20-22	16-18	DC/+	8,7-10,5
2-n'	135	1,2	200-240	21-24	16-18	DC/+	10,1-12,5
Solid wire-classification:: G2Mo according to the EN ISO 14341-A (OK AristoRod 13.09)							
Shielding gas type: Ferromix C18 – M21 according to the PN-EN ISO 14175							
Gas flow rate: [l/min]: 14 - 18				Preheat temperature: $\geq 100^{\circ}\text{C}$			
Heat treatment: not applicable				Interpass temperature: $\leq 250^{\circ}\text{C}$			

Details relating to the SAW method in the flat position – PA with a joint penetration made by the MAG method

Bead sequence	Welding process	Filler metal size [mm]	Current [A]	Voltage [V]	Travel speed [cm/min]	Polarity	Heat input [KJ/cm]
1	135	1,2	150-170	20-22	24-26	DC/+	4,9-5,6
2	135	1,2	180-200	23-25	21-23	DC/+	7,7-8,5
3	121	4,0	350-380	26-27	55-60	DC/+	8,9-9,2
4-n	121	4,0	450-500	29-31	30-32	DC/+	23,5-26,3
1'-n'	121	4,0	450-500	29-31	30-32	DC/+	23,5-26,3
135: G2Mo according to the EN ISO 14341-A (OK AristoRod 13.09)							
Solid wire-classification: 121: G3Mo according to the EN ISO 14171-A (OK AristoRod 12.34)							
Shielding gas type: Ferromix C18 – M21 according to the PN-EN ISO 14174							
Flux type: S A AB 1 67 AC H05 according to the PN-EN ISO 14175 (OK Flux 10.71)							
Drying time: 3h				Drying temperature: 300-350°C			
Gas flow rate: [l/min]: 14 - 18				Preheat temperature: ≥ 100°C			
Heat treatment: not applicable				Interpass temperature: ≤ 250°C			

was prepared where detailed welding conditions for particular processes were included. The key data of an initial manual welding technology of sample welded joints is given in tables 4, 5 and 6.

A view from the face side of the weld of fragments of welded joints made by the MAG method is shown in the picture 1a and b, while a welded joint made by the SAW method in the picture 2.

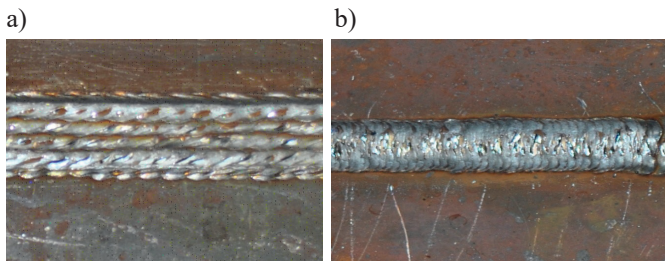


Fig. 1. A view of the face of welds made by the 135 method: a) in a horizontal position - PC, b) in a vertical upwards progression - PF



Fig. 2. A view of the face of the weld made by the 121 method in a flat position – PA

4.2. Examinations of sample welded joints

Checking a technology of welding according to the PN-EN ISO 15614-1 standard requires carrying out examinations on the sample joints in compliance with the requirements included in table 7, and relating to a given example i.e. butt joints of metal sheets with a full joint penetration.

TABLE 7

Range of control and examination of sample joints according to the PN-EN ISO 15614-1 standard [9]

Sample joint	Type of examination	Scope of examination
Butt joint with a complete joint penetration	Visual testing	100 %
	Radiographic or ultrasonic testing	100 %
	Detecting surface cracks	100 %
	Transverse tensile test	2 samples
	Transverse bend test	4 samples
	Impact strength test	2 sets required
	Hardness test	required
	Macroscopic examinations	1 sample

At first, non-destructive testing were done in a full range for all sample joints i.e. visual testing (VT), magnetic particle testing (MT), ultrasonic testing (UT), and radiography testing (RT). Taking into account requirements of the PN-EN ISO 15614-1 standard a number of examination methods was extended into a radiography testing. Tests were done after 48 hours from finishing a welding process. Quality level B was taken as an acceptance criterion according to the PN-EN ISO 5817 standard. Suitable standard specifications were used to do non-destructive testing and an inspection of joints, as well as proper acceptance criteria presented in table 8 are used.

TABLE 8

Standard specifications used to do the NDT

Examination method	Taken examinations	Acceptance criteria
Visual testing	PN-EN ISO 17637	PN-EN ISO 5817 – B
Magnetic particle inspection	PN-EN ISO 17638	PN-EN ISO 23278 – 2x
Ultrasonic testing	PN-EN ISO 17640	PN-EN ISO 11666 - 2
Radiography testing	PN-EN ISO 17636	PN-EN ISO 10675 - 1

TABLE 9

Standard specifications used to do the DT

Examination method	Taken examinations	Acceptance criteria
Tensile test	PN-EN ISO 4136	Min. $R_m = 570$ MPa
Transverse bend test	PN-EN ISO 5173	Bending angle 180°
Impact strength test	PN-EN ISO 9016	Min. $KV_{(0^\circ C)} = 65$ J
Macroscopic examination	PN-EN ISO 17639	PN-EN ISO 5817 - B
Hardness test	PN-EN ISO 9015-1	Max. 380 (HV10)

After obtaining positive results from NDT, samples were taken for destructive testing including tensile and transverse bend tests, impact strength test, macroscopic examination and hardness penetration pattern. Appropriate standard specifications were used to do destructive testing, and to make an assessment of joints, as well as relevant acceptance criteria were adopted, which is given in the table 9.

4.3. Results of examinations of sample welded joints

Taken examinations of sample welded joints according to an accepted range of examinations and acceptance criteria presented above allowed to obtain positive results of both non-destructive and destructive testing. Details of non-destructive testing are presented in table 10.

Details of the destructive testing are presented in the following tables 11 to 14.

TABLE 10

Results of the NDT of sample welded joints

Type of joint	Results of the NDT according to acceptance criteria				Comments
	VT	MT	UT	RT	
135PC/P460NH	B	2X	2	1	Lack of indications
135PF/P460NH	B	2X	2	1	Lack of indications
121PA/P460NH	B	2X	2	1	Lack of indications

TABLE 11

Results of tensile and transverse bend tests of sample welded joints

Type of joint	Results of tensile tests			Results of transverse bend tests		
	$R_{m\text{ ave}}$ [MPa]	Grade	fracture	α [°]	Grade	Cracks
135PC/P460NH	638	+	flawless	180	+	lack
135PF/P460NH	635	+	flawless	180	+	Lack
121PA/P460NH	643	+	flawless	180	+	Lack

TABLE 12

Results of the hardness test of sample welded joints

Type of joint	Average results of HV10 tests			Grade	Comments
	BM	HAZ	W		
135PC/P460NH	189	288	227	+	-
135PF/P460NH	193	246	216	+	-
121PA/P460NH	192	245	245	+	-

Tensile strength and transverse bend tests of sample welded joints made by the 121 and 135 methods (in the PC and PF positions) gave positive results with similar effects. Requirements related to the technology of welding were also fulfilled.

The highest level of hardness was found in HAZ of the joint welded by the 135 method in the PC position (the lowest level of heat input). Heat affected zone was characterised by the highest hardness in all examples. In the 121 method the same level of hardness was found both in the weld and in HAZ. Base material was characterised by the lower hardness in all examples. In all examples a level of hardness proved a regularity of the technology of welding.

The highest work of fracture was obtained in the welded joint made by the 135 method in the horizontal position PC (the lowest amount of heat input). A joint welded by the 135 method in the vertical upwards progression PF (the highest amount of heat input) was characterised by the lowest work of fracture. Joints welded by the 135 method in the horizontal PC and vertical upwards progression PF positions are characterised by a different impact strength. In case of welding in the vertical upwards progression position PF an amount of heat input is higher than in case of welding in the horizontal position PC, and therefore work of fracture is much lower in the horizontal position. Work of fracture near the HAZ in case of all sample

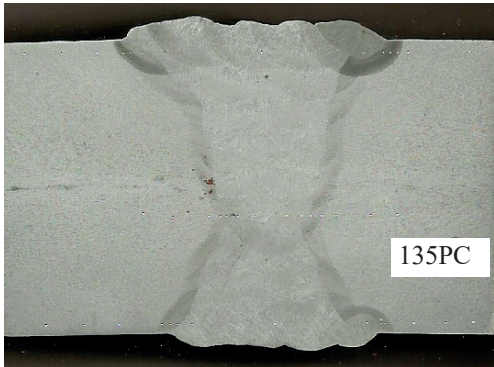
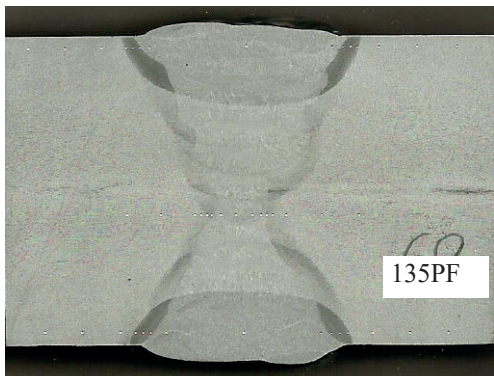
TABLE 13

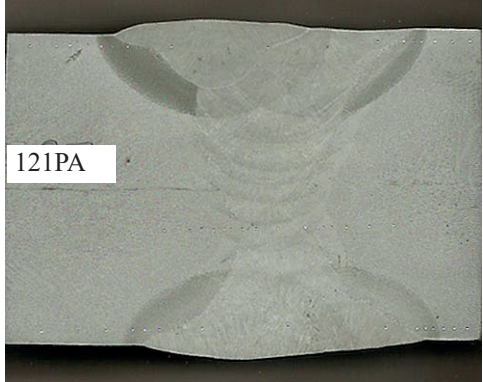
Results of impact strength of sample welded joints – work of fracture KV (0°C)

Type of joint	An area of an examination	Average results of examinations KV [J]		Grade	Comments
		W	HAZ		
135PC/P460NH	t 2	85	169	+	-
	t/2	111	177	+	-
	t-2	124	133	+	-
135PF/P460NH	t 2	69	96	+	-
	t/2	89	147	+	-
	t-2	79	161	+	-
121PA/P460NH	t 2	95	99	+	-
	t/2	103	118	+	-
	t-2	77	119	+	-

TABLE 14

Results of macroscopic examinations of sample welded joints

Type of joint	A cross-section view	Description
135PC/P460NH		Complete joint penetration. A proper fusion into a base material. A regular sequence of beads. A width of HAZ is 2,5-3,0mm. Weld's geometry and the whole joint is regular with a slight irregularity of the face of the weld. Lack of important welding defects (slight inclusions). In the central area of the base material there is a dark strip of a different structure.
135PF/P460NH		Complete joint penetration. A proper fusion into a base material. A regular sequence of beads. A width of HAZ is 2-2,5mm. Weld's geometry and the whole joint is regular. Lack of important welding defects (slight inclusions). In the central area of the base material there is a dark strip of a different structure.

121PA/P460NH		<p>Complete joint penetration. A proper fusion into a base material. A regular sequence of beads. A width of HAZ is 2-4,5mm. Weld's geometry and the whole joint is regular. Lack of important welding defects (slight inclusions). In the central area of the base material there is a dark strip of a different structure.</p>
--------------	---	--

joints obtained much higher value than in the weld. All the joints fulfilled requirements relating to the impact strength tests of examined technologies of welding.

Results of macroscopic examinations showed a proper structure of all sample joints, moreover, there were any important welding defects. Only, in the welding test of the 135 method in the horizontal position PC slight inclusions were observed. In the particular samples of welded joints there were slight differences in the width of the heat affected zone HAZ. The widest HAZ was observed in the joint welded by the 121 method.

Apart from the used method, and the welding position welded joints fulfilled the requirements of the quality level B according to the PN-EN ISO 5817 standard.

5. An assessment of welding efficiency

Sample welded joints were also assessed due to their efficiency of welding. This factor is essential not only from an economical point of view, but also thermal properties obtained in particular processes. Table 15 provides comparative results connected with efficiency of used methods of welding in examining a technology of welding fine-grained steel.

TABLE 15
An efficiency of used methods of welding

Type of sample joint	121 – PA	135 – PC	135 – PF
A number of beads of the weld	13	33	25
Time of welding 1RM of the weld [mm]	60	160	200
An average amount of heat input [KJ/cm]	25	7	10

Welding by the submerged arc (short time of welding with a relatively small amount of beads) became the most efficient. Much less efficient method of welding was the MAG-135 method in the PC position, and even less efficient appeared to be a welding test in the PF position. An efficiency of a welding process by the submerged arc in comparison to the MAG method appeared to be 2,5 times bigger. In a reverse situation there is a use of energy in particular processes, which is directly connected with a heat input.

6. Summary

On the base of taken examinations it can be assumed that the most favourable method of welding of thick-walled joints from fine-grained types of steel is a process of welding by the submerged arc (121). Mentioned method combines both a high efficiency and fulfilling all the requirements connected with mechanical properties. There is however, a certain limitation related to a possibility of welding only in the flat position (PA), therefore it prevents welding constructions of complex shapes, which require different welding positions.

Therefore, for constructions of complex shapes the most appropriate method is a submerged arc welding by the solid electrode in an active gas shield. Above method fulfils all the mechanical properties which are put on the fine-grained types of steel.

There were not any considerable differences in the quality level of welded joints in the used methods of welding. All the methods of welding allowed to obtain the highest quality level B according to the PN-EN ISO 5817 standard.

If a high impact strength of the welded joints is required, it is recommended to use the 135 method, especially in the PC position. Joints welded by the 121 method are characterised by the high impact strength of the work of fracture.

If a high plasticity, and therefore low hardness is required, than it is recommended to use the 121 and 135 methods of welding in PF positions. Above methods are characterised by the higher heat input.

Taking everything into account, it can be claimed that while choosing a proper technology of welding both quality requirements of finished joints, possibilities of implementing the process and economical issues should be considered.

REFERENCES

- [1] PN-EN ISO 4063:2011, Spawanie i procesy pokrewne – Nazwy i numery procesów
- [2] Praca zbiorowa, Poradnik inżyniera – Spawalnictwo tom II, WNT, Warszawa 2005
- [3] B. Pierozek, J. Lassociński, Spawanie łukowe stali w osłonach gazowych. WNT, Warszawa 1987
- [4] R. Krawczyk, Zakresy parametrów spawania w zależności od przeniesienia metalu w łuku spawalniczym. Biuletyn Instytutu Spawalnictwa. Nr 4/2014

- [5] J. Węgrzyn, R. Korkiewicz, *Automatyczne spawanie i napawanie pod topnikiem*, WNT, Warszawa 1966
- [6] PN-CR ISO 15608:2002, *Spawanie - Wytyczne systemu podziału materiałów metalowych na grupy*
- [7] PN-EN 10028-3:2009, *Wyroby płaskie ze stali na urządzenia ciśnieniowe - Część 3: Stale spawalne drobnziarniste normalizowane*
- [8] J. Brózda, *Stale konstrukcyjne i ich spawalność*, Instytut Spawalnictwa, Gliwice 2009
- [9] PN-EN ISO 15614-1:2008, *Specyfikacja i kwalifikowanie technologii spawania metali - Badanie technologii spawania - Część 1: Spawanie łukowe i gazowe stali oraz spawanie łukowe niklu i stopów niklu*
- [10] T. Węgrzyn, J. Piwnik, B. Łazarz, D. Hadryś, *Main micro-jet cooling gases for steel welding*, *Archives of Metallurgy and Materials* **58**, issue 2, 555 – 557 (2013).
- [11] T. Węgrzyn, J. Piwnik, D. Hadryś, *Oxygen in steel WMD after welding with micro-jet cooling*, *Archives of Metallurgy and Materials* **58**, issue 4, 1067 – 1070 (2013).
- [12] W. Tarasiuk, B. Szczucka –Lasota, J. Piwnik, W. Majewski, *Tribological Properties of Super Field Weld with Micro-Jet Process*, *Adv. Mat. Res.* **1036**, 452-457 (2014).
- [13] T. Węgrzyn, T. Piwnik, J. Wieszała, D. Hadryś, *Control over the steel welding structure parameters by micro-jet cooling*, *Archives of Metallurgy and Materials, ISS 1*, **57**, 3, 679-685 (2012).
- [14] T. Węgrzyn, *The Classification of Metal Weld Deposits in Terms of the Amount of Oxygen*. *PROC OF ISOPE, IV*, 1999, 212 – 216.
- [15] T. Węgrzyn, *The Classification of Metal Weld Deposits in Terms of the Amount of Nitrogen*. *Proceedings of ISOPE'2000, V*, 130 – 134 (2000).
- [16] B. Szczucka-Lasota, B. Formanek, A. Hernas, K. Szymański, *Oxidation models of the growth of corrosion products on the intermetallic coatings strengthened by a fine dispersive Al₂O₃*, *Journal of Materials Processing Technology* **164-165**, 935 – 939 (2005).
- [17] J. Słania, *Influence of phase transformations in the temperature ranges of 1250-1000°C and 650-350°C on the ferrite content in austenitic welds made with T 23 12 LRM3 tubular electrode*. *Metallurgy and Materials*, **3**, 2010-2014 (2005).
- [18] R. Burdzik, P. Folęga, B. Łazarz, Z. Stanik, J. Warczek, *Analysis of the impact of surface layer parameters on wear intensity of friction pairs*. *Archives of Metallurgy and Materials*, **57**, 4, 987 – 993 (2012).
- [19] K. Lukaszewicz, A. Kriz, J. Sondor: *Structure and adhesion of thin coatings deposited by PVD technology on the X6CrNiMoTi17-12-2 and X40 CrMoV5-1 steel substrates*. *Materials Science and Engineering*, **51**, 40-47.
- [20] A. Lisiecki, *Diode laser welding of high yield steel*. *Proc. of SPIE Vol. 8703, Laser Technology 2012, Applications of Lasers 87030S* (January 22, 2013), DOI: 10.1117/12.2013429.
- [21] A. Lisiecki, *Welding of titanium alloy by Disk laser*. *Proc. of SPIE Vol. 8703, Laser Technology 2012: Applications of Lasers 87030T* (January 22, 2013), DOI: 10.1117/12.2013431.
- [22] G. Golański, A. Zieliński, J. Słania, J. Jasak, *Mechanical Properties of VM12 steel after 30 000hrs of ageing at 600°C temperature*. *Archives of Metallurgy and Materials*, **59**, 2 (2014).
- [23] G. Golański, P. Gawień, J. Słania, *Examination of Coil Pipe Butt Joint Made of 7CrMoVTib10 - 10(T24) Steel After Service*, *Archives of Metallurgy and Materials*, **57**, 2, (2012).
- [24] B. Oleksiak, J. Labaj, J. Wiczorek, A. Blacha-Grzechnik, R. Burdzik, *Surface tension of cu-bi alloys and wettability in a liquid alloy - refractory material - gaseous phase system*, *Arch. Metall. Mater.* **59**(1), 281-285 (2014).
- [25] B. Oleksiak, G. Siwec, A. Blacha-Grzechnik, J. Wiczorek, *The obtained of concentrates containing precious metals for pyrometallurgical processing*, *Metalurgija* **53**(4), 605-608 (2014).
- [26] R. Burdzik, Ł. Konieczny, *Research on structure, propagation and exposure to general vibration in passenger car for different damping parameters*, *J. of Vibroengineering* **15**(4), 1680-1688 (2013).
- [27] R. Burdzik, *Research on the influence of engine rotational speed to the vibration penetration into the driver via feet - multidimensional analysis*. *Journal of Vibroengineering*, **15**, 4, 2114 – 2123 (2013).